arXiv:cond-mat/0403574v1 [cond-mat.mtrl-sci] 23 Mar 2004

Comment on "Memory Effects in an Interacting Magnetic Nanoparticle System" by Sun *et. al*, Phys. Rev. Lett. , 91, 167206 (2003)

In a recent letter Sun *et. al.*[1] have presented interesting experimental results of history dependent magnetization in a monolayer of sputtered permalloy ($Ni_{81}Fe_{19}$) clusters on a SiO_2 substrate. Starting at a high (room) temperature ($T = T_\infty$), the system is steadily cooled in a small magnetic field H and the magnetization M measured as a function of T. Subsequently at low temperatures the cooling is arrested at a few T-steps where H is first switched off and then restored after a wait of a few hours. From the lowest T the system is heated and M(T) measured in the presence of H. The heating path surprisingly shows wiggles in M(T) at all the T-steps where H was switched off during cooling, apparently keeping a memory of the temperature arrests! The authors attribute this to aging and concomitant memory-dependent effects found in the spin glass phase.

In this Comment we report (Fig.1) an identical phenomenon in systems of $NiFe_2O_4$ particles embedded in a SiO_2 matrix with two different interparticle spacings 4 nm (1) and 15 nm (2), which controls the strength of the dipolar interactions. Not only do we find the memory effect to be present in the non-interacting sample (2) (Fig.1(b)), indeed we find it to be *more* prominent than in the interacting case (1) (Fig.1(a)).

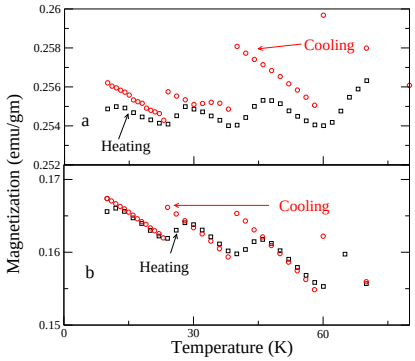


FIG. 1: Experimental M(T) curves during cooling (red) and heating (black) for the (a) interacting and (b) non-interacting cases

We demonstrate that the phenomenon observed in Ref.[1] and shown in Fig.1 can be simply attributed to a superposition of relaxation times[2]. Our calculated results, while corroborating the findings of Ref.[2], are based on a simpler model which also explains the suppression of this effect for the interacting sample. Assume that the system consists of single-domain particles of just two volumes V_1 and V_2. Recall that the characteristic relaxation time for a noninteracting single domain particle $\tau(V) \propto \exp[(KV \pm \mu HV)/k_BT]$, where K is the anisotropy energy constant, μ is the magnetic moment per unit volume, H the applied magnetic field and k_B the Boltzmann constant. We have only two relaxation times τ_1 and τ_2 associated with V_1 and $V_2 (V_2 > V_1)$. The time τ_1 is much smaller than the measurement time while τ_2 is much larger, at the lowest temperature (T_0) of measurement.

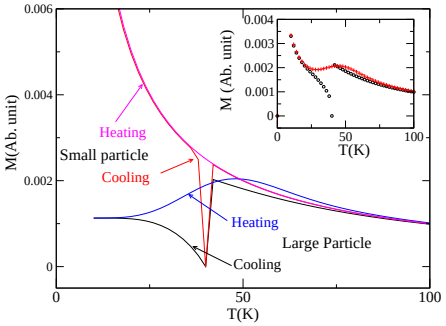


FIG. 2: Simulated arrested cooling and continuous heating for two different particle sizes. Inset shows the combined effect.

Both τ_1 and τ_2 are expected to be smaller than the measurement time at the highest temperature T_∞. Therefore, in the intermediate temperature domain ($T_0 \leq T \leq T_\infty$), some of the particles will equilibriate rapidly, thus showing superparamagnetism while the others will be 'blocked'. This is observed in Fig.2 where we have plotted M(T) separately for the two sets of particles under the same cooling and heating protocol. When H is zero, both sets of particles relax to $M = 0$, however, when H is turned on, particles 2 are blocked ($M = 0$) while 1 show facile response. As T is increased again, M for 1 decreases with T while M for 2 *increases* thus producing a wiggle. This effect is seen only when the temperature of arrest is in-between the two respective blocking temperatures. In the interacting system, one has an additional term $\propto V^2$ in the exponent of τ_V in a meanfield picture which shifts both the blocking temperatures to higher T causing the wiggles to disappear.

Discussions with P. A. Sreeram are gratefully acknowledged.

S. Chakravarty[1], A. Frydman[2], M. Bandyopadhyay[1], S. Dattagupta[1] and S. Sengupta[1]
[1] S. N. Bose National Centre for Basic Sciences, Block JD, Sector III, Salt Lake, Kolkata 700 098 INDIA.
[2] Dept. Of Physics, Bar Ilan University, Ramat Gan 52900, Israel.

[1] Y. Sun, M. B. Salamon, K. Garnier and R. S. Averback,

Phys. Rev. Lett. 91, 167206 (2003) arXiv:cond-mat/0311264 v2 9Feb 2004
[2] M. Sasaki, P. E. Jonsson, H. Takayama and P. Nordblad,