arXiv:cond-mat/0406548v1 [cond-mat.str-el] 23 Jun 2004

Weak itinerant ferromagnetism in YCo_9Si_4

H. Michor [a,*] M. El-Hagary [a] S. Özcan [a] A. Horyn [a] E. Bauer [a] M. Reissner [a] G. Hilscher [a]
S. Khmelevskyi [b] P. Mohn [b] P.Rogl [c]

[a] *Institut für Festkörperphysik, T.U. Wien, A-1040 Wien, Austria*
[b] *Center for Computational Materials Science, T.U. Wien, A-1040 Wien, Austria*
[c] *Institut für Physikalische Chemie, Universität Wien, A-1090 Wien, Austria*

Abstract

Weak itinerant ferromagnetism in YCo_9Si_4 below about 25 K is studied by means of magnetisation, specific heat, and resistivity measurements. Single crystal X-ray Rietveld refinements at room temperature reveal a fully ordered distribution of Y, Co and Si atoms within the tetragonal space group *I4/mcm* isostructural with $LaCo_9Si_4$. The latter exhibits itinerant electron metamagnetism with an induced moment of about 1 μ_B/f.u. above 6 T, whereas YCo_9Si_4 exhibits a spontaneous magnetisation $M_0 \simeq 12\,\mathrm{Am^2/kg}$ at 2 K which corresponds to an ordered moment of about 1.6 μ_B/f.u. indicating weak itinerant ferromagnetism.

Key words:
YCo_9Si_4, itinerant magnetism, specific heat

Recent interest on weak itinerant ferromagnetism e.g. in $ZrZn_2$ [1] in the context with quantum critical phenomena motivated the search for new materials showing weak itinerant ferromagnetism or being close to a ferromagnetic (FM) instability. An interesting system in this respect is the solid solution $LaCo_{13-x}Si_x$ where ferromagnetism vanishes near the stoichiometric composition $LaCo_9Si_4$ [2] where full translational symmetry (space group $I4/mcm$) is confirmed by single crystal X-ray diffractometry [3]. $LaCo_9Si_4$ is a strongly exchange enhanced Pauli paramagnet and exhibits an itinerant electron metamagnetic phase transition at about 3.5 T for $H||c$ and 6 T for $H\perp c$, which is the lowest value ever found for rare earth intermetallic compounds [3]. In this paper, we report on low temperature measurements on the isostructural and isoelectronic compound YCo_9Si_4 which was initially reported in Refs. [4,5] to be FM with $T_C \simeq 848$ K.

Polycrystalline samples of YCo_9Si_4 were synthesized by induction melting of pure elements (Y 3N, Co 4.5N, Si 6N) under protective argon atmosphere and subsequent annealing at 1050°C for one week. The phase purity and composition has been verified by means of electron microprobe analysis. The crystal structure was determined by means of single crystal X-ray diffraction ($R_{F^2} = 2\%$) revealing a fully ordered distribution of Y, Co and Si atoms with the $LaFe_9Si_4$-type [6] with a single rare earth site, three cobalt sites and again a single Si site. The lattice parameters are $a = 7.754(1)$ Å and $c = 11.487(1)$ Å at room temperature (see Ref. [3] for experimental details). Crystallographic order is also corroborated by a reasonably low residual resistivity $\rho_0 = 7\mu\Omega$cm (see below).

Temperature and field dependent magnetisation measurements $M(T,H)$ on YCo_9Si_4 depicted in Fig. 1 as an Arrott plot M^2 versus H/M reveal weak ferromagnetism below about 25 K with an extrapolated spontaneous magnetisation $M_0 \simeq 12\,\mathrm{Am^2/kg}$ at 2 K (see the dashed line in Fig. 1) corresponding to

* Corresponding Author: Email: michor@ifp.tuwien.ac.at
[1] The work was supported by the Austrian Science Foundation Fonds, P-15066-Phy. M. El-H. is on leave from Helwan University, Cairo, Egypt. A.H. is on leave from Ivan Franko Lviv National University, Lviv, Ukraine, with support from ÖAD.

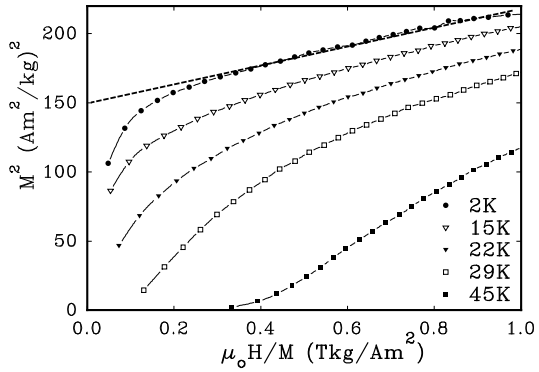


Fig. 1. Arrott plot M^2 vs. H/M of isothermal magnetization data of YCo_9Si_4.

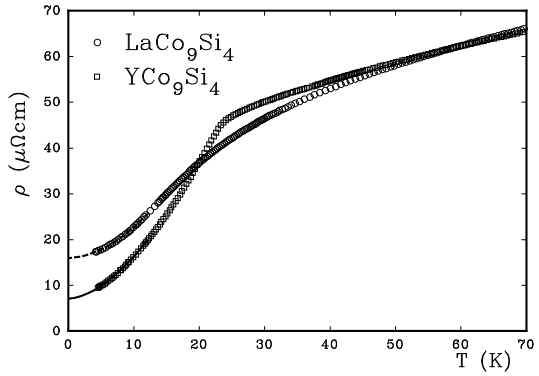


Fig. 2. Temperature dependent resistivity $\rho(T)$ of YCo_9Si_4 and $LaCo_9Si_4$; dashed and solid lines are fits, see text.

$1.6\,\mu_B$/f.u. and a longitudinal susceptibitity in the FM regime, $\chi_0 \sim 0.25\,\mathrm{Am^2/kgT}$, determined from the $\mu_0 H/M$ axis intercept of the dashed line extrapolation in Fig. 1. The Curie-temperature T_C is around 25 K in reasonable agreement with specific heat and transport anomalies (see below).

The temperature dependent resistivity $\rho(T)$ of YCo_9Si_4 shown in Fig. 2 reveals a significant change of slope around about 25 K which is associated with the onset of ferromagnetism. Below about 15 K, in the FM state, $\rho(T)$ is well described by a power law behavior $\rho(T) = \rho_0 + AT^\alpha$ (see the solid line in Fig. 2) with $\rho_0 = 7\mu\Omega$cm, $A = 0.176\mu\Omega\mathrm{cm/K}^{-\alpha}$ and $\alpha = 1.72$. The corresponding fit for nearly ferromagnetic $LaCo_9Si_4$ (dashed line in Fig. 2) yields $\rho_0 = 16\mu\Omega$cm, $A = 0.085\mu\Omega\mathrm{cm/K}^{-\alpha}$ and $\alpha = 1.9$ indicating a spin fluctuation (Fermi liquid) regime for the latter compound.

The specific heat of YCo_9Si_4 and (for comparison) $LaCo_9Si_4$ is shown in Fig. 3 as C/T vs. T revealing for both compounds a relatively large electronic Sommerfeld value γ close to $200\,\mathrm{mJ/mol\,K^2}$ and in the case of YCo_9Si_4 a small somewhat broadened anomaly associated with the second order phase transition towards

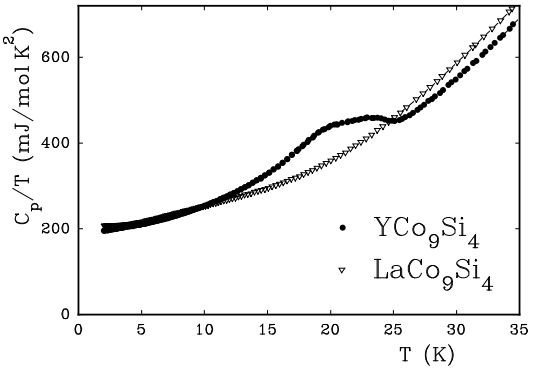


Fig. 3. Temperature dependent specific heat as C/T vs. T of YCo_9Si_4 and $LaCo_9Si_4$.

weak itinerant ferromagnetism with a jump $\Delta C/T$ of the order of $100\,\mathrm{mJ/mol\,K^2}$ in approximate agreement with the Stoner-Wohlfarth model (see e.g. Ref. [7]) yielding $\Delta C/T_C = M_0^2/\chi_0 T_C^2 \sim 70\,\mathrm{mJ/mol\,K^2}$. In the case of exchange enhanced Pauli paramagnetic $LaCo_9Si_4$ the value of $\gamma \simeq 200\,\mathrm{mJ/mol\,K^2}$ can be compared with the density of states obtained from *ab-initio* electronic structure calculations, $N(E_F)$ ∼19 states/eV f.u., revealing a spin-fluctuation mass enhancement $\lambda_{spin} \sim 3.3$ [3].

For YCo_9Si_4 band calculations have been performed in the same manner as described in Ref. [3] for $LaCo_9Si_4$ yielding practically the same picture with respect to the Co d-bands as for $LaCo_9Si_4$ and within the numerical accuracy the same density of states at the Fermi level. The spin-fluctuation mass enhancement λ_{spin} is thus very similar in YCo_9Si_4 and $LaCo_9Si_4$. Band calculations at the experimental lattice constant yield a FM ground state for both compounds, which is experimentally confirmed only for YCo_9Si_4 while $LaCo_9Si_4$ shows a paramagnetic ground state and metamagnetism. In analogy to the conclusions drawn for $LaCo_9Si_4$ we expect also for YCo_9Si_4 in the FM state the largest moments of about 0.3–0.4 μ_B/Co to be at the 16k Co-sites and significantly smaller moments at the 4d and 16l Co-sites.

References

[1] C. Pfleiderer *et al.*, Nature (London) **412** (2001) 58.

[2] M. El-Hagary *et al.*, J. Alloys Compounds **367** (2004) 239.

[3] H. Michor *et al.*, Phys.Rev. B **69** (2004) 081404(R).

[4] R.V. Skolozdra *et al.*, J. Alloys Compounds **296** (2000) 272.

[5] Yu. Gorelenko *et al.*, Visnyk of the Lviv University, Series Chemical **43** (2003) 62.

[6] W.H. Tang *et al.*, J. Appl. Phys. **76** (1994) 4095.

[7] P. Mohn and G. Hilscher, Phys.Rev. B **40** (1989) 9126.